

TEST REPORT

No. : GZIN2506001030CM01_EN

Date : 2025-10-21

Page: 1 of 4

CUSTOMER NAME: Foshan Vipostone Co., Ltd.
ADDRESS: No. 6-3, Yuyang Road 1, Huyong Industrial Zone, Nanzhuang Town,
Chancheng District, Foshan City

Sample Name : Flexible Stone
Product or Lot No. : 20250525
Other Information : 300*300/300*600/400*800/600*1200/1200*2400/1200*2800/1200*3000

Above information and sample(s) was/were submitted and confirmed by the client. SGS, however, assumes no responsibility to verify the accuracy, adequacy and completeness of the sample information provided by client.

Date of Receipt : 2025-06-12
Testing Period : 2025-06-12 ~ 2025-10-21
Test result(s) : For further details, please refer to the following page(s)
(Unless otherwise stated the results shown in this test report refer only to the sample(s) tested)

Signed for
SGS-CSTC Standards Technical
Services Co., Ltd. Guangzhou
Branch.

Tobby Yang
Authorized signatory

TEST REPORT

No. : GZIN2506001030CM01_EN

Date : 2025-10-21

Page: 2 of 4

Summary of Results:

No.	Test Item	Test Method	Result
1	Light Ageing Test-UV Exposure	ASTM G154-23 Cycle 1	See result

DRAFT

TEST REPORT

No. : GZIN2506001030CM01_EN

Date : 2025-10-21

Page: 3 of 4

1. Test Item: Light Ageing Test-UV Exposure

Sample Description: A-Panel

Test Method: ASTM G154-23 Cycle 1

Test Condition:

Exposure Cycle:

Lamp Type: UVA-340

8h UV at (60±3)°C BPT, 0.89W/(m²·nm)@340nm

4h condensation at (50±3)°C BPT

Exposure Time: 3000h

Lab Environmental Condition: (23 ± 2) °C, (50 ± 5) %RH

Test Result:

Sample A

Specimen	ΔE^*_{ab}		Gray scale
	SCI	SCE	
1	0.76	0.89	4-5
2	0.33	0.40	4-5
3	0.34	0.45	4-5

Note:

1. According to ASTM D2616-19, the gray scale was determined under the D65 standard light, with scale 5 as the best and scale 1 as the worst.

2. According to ASTM D2244-25, ΔE^*_{ab} was measured by sphere spectrophotometer d/8° under D65 standard light source and with 10° observer. SCI: include specular component reflection condition, SCE: exclude specular component reflection condition, 25mm aperture.


TEST REPORT

No. : GZIN2506001030CM01_EN

Date : 2025-10-21

Page: 4 of 4

Test Photo:

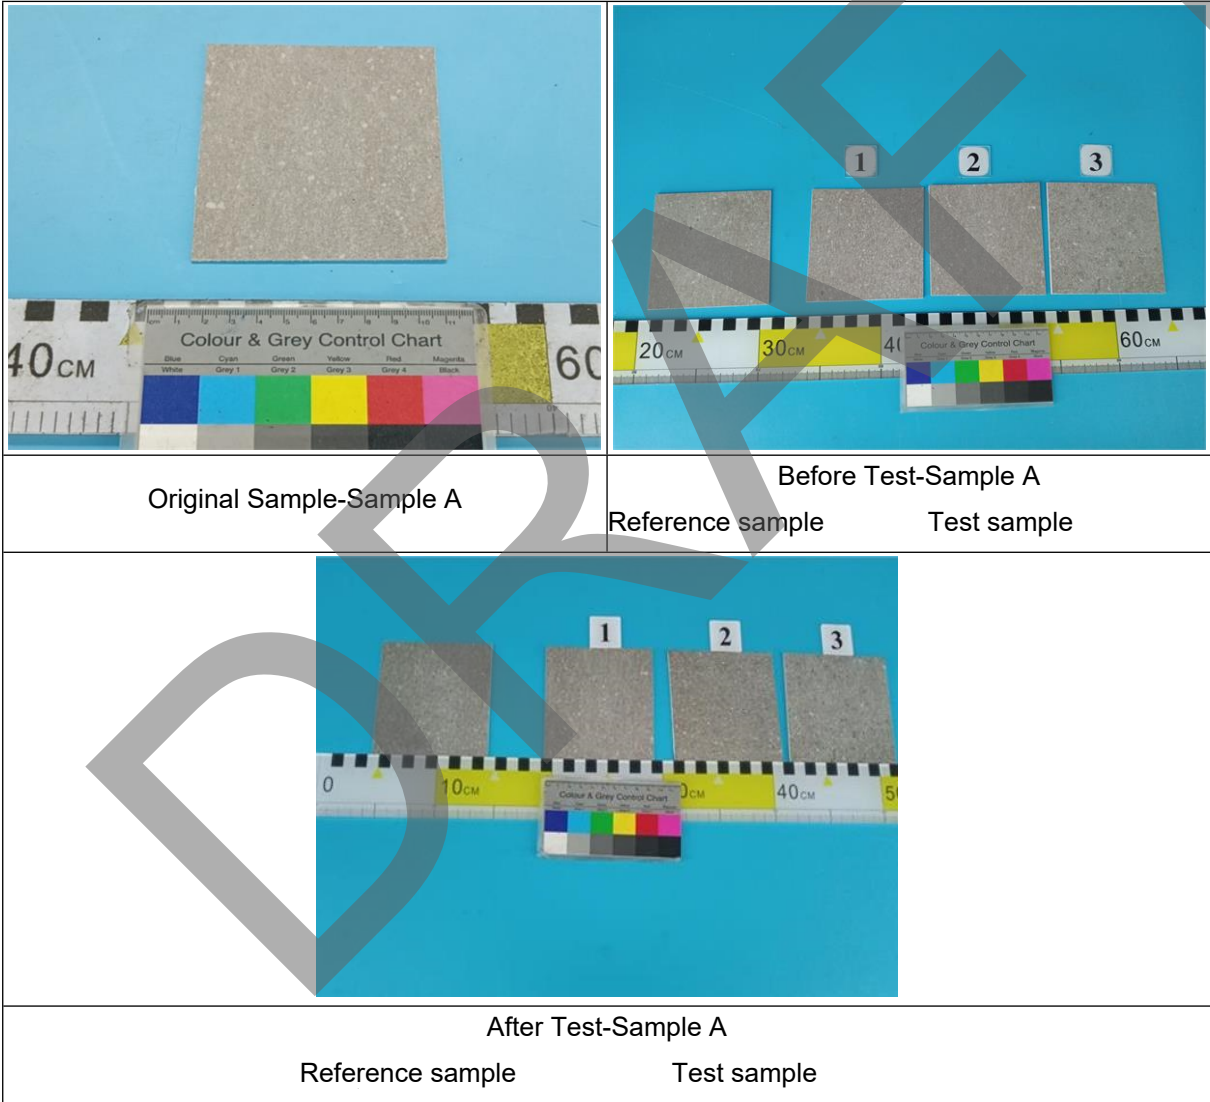

Appendix information:

The test report shall only be used for client scientific research, teaching, internal quality control, product research and development, etc. and just for client internal reference.

*****End of report*****